

# To Study the Mechanical Behavior of Friction Welding of HSS M<sub>33</sub> & SS 316

Gourav Sardana<sup>1</sup>, Ajay Kumar<sup>2</sup>

<sup>1</sup>M.tech Student, Mechanical Department, O.I.T.M, Hissar, Haryana, India, [gourav.sardana@yahoo.com](mailto:gourav.sardana@yahoo.com)

<sup>2</sup>Asst. professor, Mechanical Department, O.I.T.M, Hissar, Haryana, India, [apkumar12@gmail.com](mailto:apkumar12@gmail.com)

## Abstract

*The purpose of this work was to join and assess the development of solid state joints of dissimilar material HSS M<sub>33</sub> and AISI 316 stainless steel, via continuous drive friction welding process, which combines the heat generated from friction between two surfaces and plastic deformation. Experiments performed on manually lathe machine with different three rpm (1700, 2700, and 3700) & different position of work pieces Tests were conducted with different welding process parameters. The strength of the welded joint was determined by Breaking Point load. Micro hardness values of the joints were also obtained with the HV hardness scale. The microstructures of welded joint also study with the help of Optical Microscope.*

*Index Terms:* Friction welding, welding parameters, Mechanical characterization, Metallographic.

\*\*\*

## 1. INTRODUCTION

Welding technology is used in manufacturing development of New welding method. Welding of different metal and their alloys is a common application in engineering. "Friction welding" (FW) is a group of solid-state [welding] processes using heat generated through mechanical friction between moving work pieces, with the addition of an upsetting force to plastically displace material. This technique, which we refer to as "friction welding" provides a very simple method of joining a probe to a work piece. Friction welding is a type of forge welding, i.e. welding is done by the application of pressure. Friction generates heat, if two surfaces are rubbed together, enough heat can be generated and the temperature can be raised to the level where the parts subjected to the friction may be fused together. The principle of this process is the changing of mechanical energy into heat energy. One component is gripped and rotated about its axis while the other component to be welded to it is gripped and does not rotate but can be moved axially to make contact with the rotating component. At a point fusion temperature is reached, then rotation is stopped and forging pressure is applied. Then heat is generated due to friction and is concentrated and localized at the interface, grain structure is refined by hot work.

**Material and Method used in friction welding:** The material used in experiment was HSS & SS .All the specimen were made in cylindrical shape having diameter 10mm & length 130mm. Experiments performed on manually lathe machine &

special type of fixture is used on the lathe machine to estimate the manually forge pressure.

### 1.1 Continuous Drive Friction Welding

The present study utilized a continuous drive friction welding machine. In continuous drive friction welding one work piece is rotated at nominal constant speed in action alignment with the second part under an applied pressure. The rotation and pressure are maintained for the specific period to ensure adequate thermal and mechanical conditioning of the interface region. Thereafter, the rotation is stopped often with forced braking and at the same time pressure is increased to upset parts together. The application of an axial force maintains intimate contact between the parts and causes plastic deformation of the material near the weld interface.



Fig.1 (Friction Welding of HSS &amp; SS)

## 2. EXPERIMENTAL SETUP DETAIL

Manually Lathe machine is used for the friction welding operation. Machine setup is done as per the principle of continuous drive friction welding machine & to measure the forge pressure hydraulic jack with pressure gauge is used in the tail stock. So that manually effort can be measured. The main condition of machine that work pieces must be ideal alignment as shown in Figure.2 otherwise work pieces may be damage.

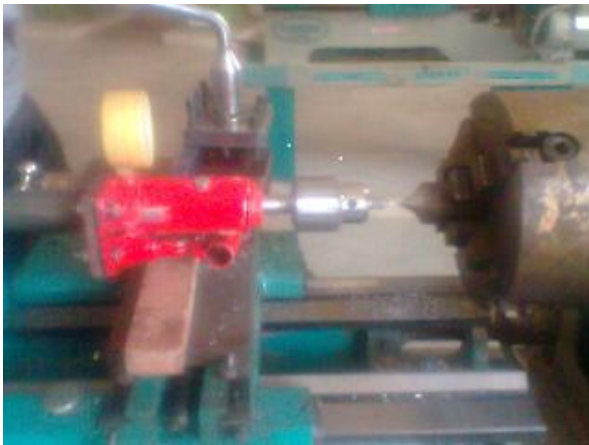


Fig.2 (Ideal alignment of Fixture)

### 2.1 Chemical composition of Base Metal

Element	%
Fe	74.23
C	1.07
Si	.520
Mn	0.277
P	0.0230

S	0.006
Cr	3.85
Mo	9.37
Ni	0.224
Al	< 0.01

Table1: (Chemical composition of HSS)

Element	%
Fe	68.41
C	0.022
Si	0.550
Mn	1.37
P	0.0350
S	.022
Cr	16.54
Mo	2.07
Ni	10.39
Al	0.015

Table2: (Chemical composition of SS)

### 2.2 Experiment Procedure

First of all machine is set up as per requirement of Friction welding i.e. Fixture is arranged on the machine. High speed steel and stain less steel is used for the friction welding. Experiments performed with three different rpm (1700, 2700, and 3700). One of the component (HSS) is at rpm & other (SS) stationary in the fixture. Heat is generated during the friction between the two materials (HSS & SS). Temperature gun is used to measure the temperature during the friction welding process. Stop watch is used to measure the Friction time of welding operation of two different materials (HSS & SS).total Six experiments performed on three different rpm (1700, 2700, 3700 ) & different position of work pieces(HSS rpm –SS constant) as shown in table.3 & sample in figure .3

sample	Rpm	Position	Forge pressure (kg/cm <sup>2</sup> )	Friction Time (sec)	Forge Time (sec)	Temp (°C)
S <sub>1</sub>	1700	HSS(rpm) SS(const)	100	7	35	850

S <sub>2</sub>	2700	HSS(rpm) SS(const)	150	7	30	880
S <sub>3</sub>	3700	HSS(rpm) SS(const)	180	7	24	920
S <sub>4</sub>	3700	HSS(const) SS(rpm)	330	14	48	965
S <sub>5</sub>	2700	HSS(const) SS(rpm)	210	14	75	895
S <sub>6</sub>	1700	HSS(const) SS(rpm)	110	14	150	870

Table .3(Experiment record)

Fig.3 Samples (S<sub>1</sub>-S<sub>6</sub>)

### 3. RESULTS & DISCUSSION

**3.1 Breaking Point Test:** The Breaking point Test of friction welded specimens was performed on the Universal Testing Machine 50 ton U.T.M Breaking point value given in Table no.4:

Sample No	Breaking Load (KN)
S <sub>1</sub>	9.96
S <sub>2</sub>	9.10
S <sub>3</sub>	3.30
S <sub>4</sub>	3.54
S <sub>5</sub>	2.92
S <sub>6</sub>	3.82

Table.4 (Breaking load value)

When rpm is increased from 1700 to 2700 (HSS rpm & SS constant) breaking load value is decreased from 9.96 - 9.10(KN).& when further rpm is increased from 2700 to 3700

### 3.3 Microstructure Examination of Friction Welded

**Joints:** Microstructure of the specimens was captured on an Optical Microscope at 500X magnification with the help of a camera along the weld. Images were captured at different places along the weld, on interface, very near to the interface on High Speed steel side, very near to the interface on Stainless Steel side, on High speed steel and on Stainless Steel as shown in Fig.3

then breaking load value simultaneously decreased up to 3.30 (KN).

When rpm is increased from 1700 to 2700 (HSS constant & SS rpm) breaking load value is decreased from 3.82 -2.92 (KN) & when further rpm is increased from 2700 to 3700 then breaking load value is increased up to 3.54 (KN).

### 3.2 Micro Hardness Measurements of Friction Welded

**Joints:** Micro hardness measurement of the specimens was done along the weld and at the cross section of base metal. Stainless steel and High Speed steel was taken along the weld hardness. On High Speed Steel and on stainless steel hardness was taken at a constant distance of 0.10mm from the interface in all samples. Total of 12 readings were taken, one on intersection, 6 on High Speed Steel side and 6 on Stainless Steel side as shown in table 5&6.


Sample No	Distance From SS Side(mm)	Hardness(HV.3)
S <sub>1</sub>	.10	312-316
S <sub>2</sub>	.10	300-305
S <sub>3</sub>	.10	310-315
S <sub>4</sub>	.10	326-335
S <sub>5</sub>	.10	325-330
S <sub>6</sub>	.10	320-325

Table.5

Sample No	Distance From HSS Side(mm)	Hardness(HV.3)
S <sub>1</sub>	.10	440-450
S <sub>2</sub>	.10	390-400
S <sub>3</sub>	.10	290-300
S <sub>4</sub>	.10	270-280
S <sub>5</sub>	.10	260-270
S <sub>6</sub>	.10	240-250

Table.6


Higher Hardness values are observed next to interface but they dramatically decreased with increase distances. As rpm is increases temp is also increases & hardness is also increases. But hardness is decreases with increases the upset time. Micro hardness value in the weld zone was much higher then the parents' material. Hardness increase with decreasing particle size.



Micro structure of HSS



Micro structure of SS



Micro structure of HSS &amp; SS

Fig.3

The micro structure of base metal consists of austenitic grain structure. Micro photograph shows that Stainless steel was greatly deformed with grains elongated & refined near the weld inter face. Micro structure of stainless steel consists of austenitic grains & High speed steel structure consists of carbide particles in marten site matrix.

#### 4. CONCLUSION

In general terms, the present invention is dependent on continuous drive (one piece in rotation & other in linear motion) where both faces of the weld joint are in motion during the heating phase of the operation, which motions are brought into phase when the conditions of the joint are appropriate. The change of phase of the motions of the mating parts can be accomplished with highly precision and speed than are possible when alignment of the parts is dependent on stopping the motion of one or both the parts. Friction welding has been successfully employed to weld dissimilar metals. Strength of the joints obtained was good. As we increases the rpm (HSS rpm & SS constant) of job then breaking point load is decreases but when rpm (HSS constant & SS rpm) of job then breaking point load is increases at high rpm.

#### REFERENCES

- [1]. A. Kurt, Iuygur & U.Palasan “Effect of Friction welding Parameter on Mechanical & Micro structural properties of dissimilar AISI 1010-ASTM B22 joints”, Journal of Welding Research May 2011, Vol 90.
- [2]. G.Kiran Kumar, K.Kishore & P.V .Gopal Krishna “Investigating the capabilities of medium duty lathe for friction welding”, Journal of Emerging Trends in Engineering and applied Sciences (JETEAS) 1(1) 2010.
- [3]. Ihsan Kirik, Niyazi Ozdermir, Ugur Caligulu “Examination of Microstructure and Mechanical Properties of Friction welded joints of medium Carbon steel to austenitic stainless steel” Published in 14<sup>th</sup> International Materials Symposium (IMSP2012).
- [4]. Imran Bhamji, Michael Preuss, Philip L.Threadgill, Richard J.moat “Linear Friction welding of AISI 316 L Stainless steel”, Journal of Materials Science and Engineering A 528 (2010).
- [5]. Mumin Sahin “Joining with friction welding of High speed steel and Medium Carbon Steel”, Journal of Materials forecasting Technology 168, 2005.
- [6]. Mumin Sahin “An investigation into joining of austenitic stainless steels (AISI304) with friction welding” Assembly Automat 25(2), 2005.
- [7]. Ranjan Sahoo & Pinaki Samantaray “Study of friction welding” Thesis of N.I.T, Rourkela 2007.
- [8]. Shubhavardhan RN “Friction Welding to join the dissimilar metals”, International Journal of Emerging technology and Advanced Engineering vol .2, issue 7, 2012.
- [9]. Mumin sahin & Cenk misirli “Mechanical & metallurgical properties of friction welded aluminium joints”, published in New Trends in Fabrication & applications book edited by zaki Ahmad, 2012.
- [10].Ali Moarrefzadeh “Study of Heat Affected Zone in Friction welding process.” Journal of Mechanical Journal of Mechanical Engineering vol .1No.1.2012.
- [11]. Eder Paduan Alves “Welding of AA1050 aluminium With AISI 304 stainless steel by rotatry friction Welding process” journal of aerospace management Technology .vol.2no.2.2010.
- [12]. I. Bhamji, R.J Moat, M.preuss, Philip L.Threadgill “Linear friction welding of Al & Mg” Journal of Science & Technology of welding& joining Vol 17, No 12, 2012.
- [13]. Ozdermir N. “Investigation of the mechanical Properties of friction-welded joints between AISI 304L and AISI 4340 steel as a function Rotational speed”, Materials Letters, 59:2504-2509, 2005.
- [14]. S.Vardhanlalam, G. mahusudhan Reddy, T.Mohandas “Continuous Drive friction Welding of iniconel 718 and EN 24 dissimilar metal Combination”, Journal of Materials Sciences and Technology 2009 vol 25.